

Infrared study of spin crossover Fe-picolylamine complex

Hidekazu OKAMURA*, Masato MATSUBARA, Takeshi TAYAGAKI¹, Koichiro TANAKA¹,
Yuka IKEMOTO², Hiroaki KIMURA² Taro MORIWAKI² and Takao NANBA,

Graduate School of Science and Technology, Kobe University, Kobe 657-8501

¹*Department of Physics, Graduate School of Science, Kyoto University, Kyoto 606-8502*

²*Japan Synchrotron Radiation Research Institute, Sayo 679-5198.*

(Received February 2, 2008)

Infrared (IR) absorption spectroscopy has been used to probe the evolution of microscopic vibrational states upon the temperature- and photo-induced spin crossovers in $[\text{Fe}(\text{2-picolylamine})_3]\text{Cl}_2\text{EtOH}$ (Fe-pic). To overcome the small sizes and the strong IR absorption of the crystal samples used, an IR synchrotron radiation source and an IR microscope have been used. The obtained IR spectra of Fe-pic show large changes between high-spin and low-spin states for both the temperature- and the photo-induced spin crossovers. Although the spectra in the temperature- and photo-induced high-spin states are relatively similar to each other, they show distinct differences below 750 cm^{-1} . This demonstrates that the photo-induced high-spin state involves microscopically different characters from those of the temperature-induced high-spin state. The results are discussed in terms of local pressure and structural deformations within the picolylamine ligands, and in terms of their possible relevance to the development of macroscopic photo-induced phase in Fe-pic.

KEYWORDS: spin crossover complex, photo-induced phase transition, infrared spectroscopy, infrared synchrotron radiation

1. Introduction

Recently, photo-induced spin crossover (SC) phenomena have attracted a lot of interest in the condensed matter physics community. Various compounds have been shown to exhibit photo-induced SC, many of which are organic complexes containing transition metal elements. $[\text{Fe}(\text{2-pic})_3]\text{Cl}_2\text{EtOH}$ (2-pic = 2-picolylamine = 2-aminomethyl pyridine, EtOH = ethanol), hereafter referred to as Fe-pic, is one of such spin-crossover compounds.¹⁻⁵⁾ As illustrated in Fig. 1(a), in Fe-pic an Fe^{2+} ion is coordinated by three 2-picolylamine ligands, where Fe^{2+} is octahedrally surrounded by nearest neighbor N atoms. A picolylamine molecule is sketched in Fig. 1(b). Four formula units of $[\text{Fe}(\text{2-pic})_3]\text{Cl}_2\text{EtOH}$ are contained in a unit cell. Two different electron configurations are possible for Fe^{2+} , depending on the Hund coupling among the $3d$ electrons and the crystal field splitting, as sketched in Fig. 1(c). If the former is greater, Fe^{2+} takes the total spin $S=2$ (“high-spin” state), and otherwise it takes $S=0$ (“low-spin” state), where the Fe-N bond length is larger in $S=2$ state. Fe-pic undergoes a SC from $S=2$ to 0 upon cooling through $T_c \sim 115\text{ K}$ as shown in Fig. 1(d), where γ_{HS} , the fraction of high-spin Fe^{2+} ions deduced from the measured magnetic susceptibility, is plotted as a function of temperature.⁸⁾ Far below T_c , the conversion to $S=0$ is almost complete. The SC occurs in a temperature width of about 30 K. (The plateau-like structure seen in the middle of crossover in γ_{HS} is of great interest,⁹⁾ but not discussed in this work.) Below T_c , a photoexcitation can cause a crossover back to $S=2$. At low temperatures, this photo-induced $S=2$ state has a long lifetime even after the photoexcitation is turned off, reaching a few hours at 10 K. Hereafter, we refer

to these three characteristic states of Fe-pic as follows: the high-temperature, high-spin ($S=2$) state above T_c as “HTHS”, the low-temperature, low-spin ($S=0$) state below T_c as “LTLS”, and the photo-induced, high-spin ($S=2$) state below T_c as “PIHS”.

A stabilization of high-spin state under photoexcitation at low temperatures has been found for many different SC compounds, and referred to as the “light-induced excited spin-state trapping”. In the case of Fe-pic, the development of PIHS has a characteristic threshold for the photoexcitation intensity, and an incubation time exists between the start of photoexcitation and the appearance of PIHS.⁴⁾ In addition, the relaxation of PIHS to LTLS is strongly non-exponential.³⁾ These characteristic features strongly suggest that the appearance of PIHS in Fe-pic involves a collective interaction among the Fe^{2+} ions. Because of this, it has been suggested that the appearance of PIHS in Fe-pic should be a transition to a new macroscopic phase under photoexcitation, referred to as the “photo-induced phase transition”.⁵⁾ Its general understanding is the following: After the photoexcitation of low-spin Fe^{2+} ions to high-energy states, some of them relax to the high-spin state, instead of relaxing directly to the initial low-spin state. Since the relaxation to the high-spin state involves a large lattice deformation (expansion), it may have a long lifetime when the thermal fluctuation is quenched at low temperatures. Because of this, the density of high-spin Fe^{2+} ions increases with time. When it reaches a critical value, the local deformations at different Fe^{2+} sites act collectively, leading to the development of PIHS over a macroscopic volume. However, the microscopic nature of the PIHS has not been understood well. For example, there has been a lot of discussion whether or not the PIHS and the HTHS are the identical $S=2$ states. In addition, it is not well

* E-mail: okamura@phys.sci.kobe-u.ac.jp

known how the local deformations at the FeN_6 clusters lead to a long-range, collective interaction among them required for the development of PIHS.

To answer the above questions, it is important to obtain microscopic information about the electronic and vibrational states of Fe-pic in the three states. For this purpose, both Raman and infrared (IR) spectroscopies have been performed.⁵⁻⁷⁾ Raman spectroscopy has the advantage of being able to use resonance effects by tuning the incident photon energy, which is particularly useful in studying transition-metal complexes such as Fe-pic. Indeed, the Raman studies of Fe-pic have provided much insight into the microscopic properties of Fe-pic. With the IR spectroscopy, one can use very low intensity and small photon-energy for the incident beam. This is also useful for the study of photo-induced SC, since one can separate the photoexcitation source and the probe IR source. Previous IR works of Fe-pic⁵⁻⁷⁾ had been performed on powder samples pressed into KBr pellets. This was due to the small sizes (typically less than 1 mm) of the crystalline Fe-pic, and due to its very strong absorption in the mid-IR range. Fe-pic is a soft material, and is very easily oxidized. Hence with powder samples, there is a risk of obtaining extrinsic effects arising from surface oxidization, stress and strain caused by pressing, and also from size effects when using long-wavelength IR radiation. (Wave numbers below 2000 cm^{-1} correspond to wavelengths longer than $5\text{ }\mu\text{m}$, which may be well comparable to the powder sizes.) Hence it is strongly desired to use crystalline samples to obtain the intrinsic bulk information.

In this work, we have studied in detail the IR absorption of Fe-pic using bulk crystal samples at various temperatures and under photoexcitation, to obtain intrinsic information about the microscopic vibrational states of Fe-pic. To overcome the above-mentioned difficulties with using crystal samples, we have used a synchrotron radiation IR source and an IR microscope. Many absorption lines have shown marked changes in the intensity and/or the peak position upon the temperature- and photo-induced SC's. In addition to the strong absorption lines previously observed with powder samples, we have newly found many weak lines that also show marked variations upon SC's. Although the absorption spectra are relatively similar between HTHS and PIHS, there are clearly different spectral features below 720 cm^{-1} . Namely, HTHS and PIHS involve microscopically different nature. We will discuss the implications of this result.

2. Experimental

The crystal samples of Fe-pic used in this work were grown by an evaporation method. Plate-shaped samples with a typical size of $0.5 \times 0.5 \times 0.1\text{ mm}^3$ were used. The IR spectroscopy was performed using a synchrotron radiation source and an IR microscope at the beam line BL43IR of SPring-8.^{10,11)} Since the synchrotron radiation is emitted from an electron beam, the effective source size is much smaller than the conventional source. When focused onto the sample through the microscope, a spot diameter as small as $15\text{ }\mu\text{m}$ was obtained without using any aperture or pin-hole. To achieve the same

spot size with a conventional IR source, it would be necessary to place a small pin-hole within the optical path, which should result in much smaller intensity. With such low intensity of incident IR beam, it would be impossible to study the transmission spectra of Fe-pic, which is strongly absorbing in the mid-IR range. To cool the sample a liquid He continuous flow cryostat was used, and to record the IR spectra a Fourier transform IR interferometer and a HgCdTe detector were also used.

3. Results and Discussion

In Section 3.1 the measured IR spectra of Fe-pic are presented as a function of temperature on going from HTHS to LTLS. In Section 3.2, the IR spectra after photoexcitation are presented, and the spectra in the three states are compared to one another. In Section 3.3, first the observed IR lines are assigned to specific vibration modes of Fe-pic, and then the discussion will be given.

3.1 IR spectra of Fe-pic as a function of temperature

Figure 2 shows the optical density (OD) spectra of Fe-pic at temperatures above and below T_c recorded without photoexcitation. OD is a measure of absorption, given as $-\log[I(\nu)/I_0(\nu)]$, where ν is the wave number, $I(\nu)$ is the transmission spectrum of the sample and $I_0(\nu)$ is the reference spectrum recorded without sample. The detection limit for a weak transmission was about $\text{OD}=2.7$ when the accumulation time was 2 min, and Fig. 2 shows the spectra below $\text{OD}=2.5$ only. A large number of absorption lines are observed in Fig. 2, which are basically due to intramolecular vibration modes of picolylamine, ethanol, and FeN_6 clusters. Intermolecular or lattice vibrations should have much lower frequencies, since they involve vibrations of the entire Fe-picolylamine complex. With decreasing temperature from above to below T_c , hence going from HTHS ($S=2$) to LTLS ($S=0$), some of the lines show large variations in their intensities and/or frequencies. In Fig. 2, some of such absorption lines are indicated by the shaded areas. Note that those at $600\text{--}750\text{ cm}^{-1}$ show particularly large temperature variations. In addition, weak but characteristic lines have been observed at $2150\text{--}2400\text{ cm}^{-1}$, as shown in Fig. 3. These lines also show very large intensity changes with decreasing temperature. The strong absorption lines seen in Fig. 2 had been already observed in the previous work based on powder samples,^{6,7)} but many of the weak lines in Figs. 2 and 3 had been overlooked.

Figure 4 shows the temperature dependence of the intensity for several absorption lines seen in Figs. 2 and 3. For each curve, the intensity integrated over the wave number range indicated in the figure has been normalized by the difference between 40 and 200 K. It is very clear that the intensity variations during the SC closely follow that of γ_{HS} , shown in Fig. 1(d). In particular, the temperature width over which the intensity changes is as narrow as that in γ_{HS} . Apparently, the vibration modes giving rise to these absorption lines are strongly coupled with the spin state of Fe^{2+} . In the previous work with powder samples,⁷⁾ the intensity change of an IR absorption line during the SC was observed much broader than that in γ_{HS} . Hence the present data based on the crys-

tal samples appear to provide more intrinsic information regarding the microscopic vibrational states in Fe-pic.

3.2 IR spectra in the PIHS, and comparison with those in the other two states

Figure 5 shows the IR absorption spectra of Fe-pic in LTLS and PIHS at 10 K, which were recorded before and after a photoexcitation for 5 min, respectively. Some of the observed IR lines have been labeled by the letters *a* to *i* in Fig. 5. The photoexcitation was made by a white light from a tungsten lamp with a power density of ~ 1 mW/mm², and it was turned off before the data accumulation. The white light had a broad spectral distribution from visible to near-IR, which covered a wide photon energy range below the absorption edge of Fe-pic. Hence the excitation light had a large penetration depth and the photoexcitation was made uniformly within the sample volume. The PIHS of Fe-pic has a long lifetime at 10 K, and indeed the IR absorption spectra measured immediately after and 5 min after the turn-off of the excitation source were nearly identical. In Fig. 5, many of the lines exhibit marked variations upon photoexcitation. Particularly strong variations are evident for the lines below 750 cm⁻¹, those around 1200 cm⁻¹ and 1600 cm⁻¹, and those between 2200 and 2400 cm⁻¹. Since the sample temperature is the same for the two spectra, these spectral variations are purely due to changes in the microscopic vibrational states caused by the photo-induced SC.

Figure 6 compares the IR spectra in HTHS (140 K) and PIHS (10 K). The spectrum in PIHS is the same as that in Fig. 5, and the line labels are also the same as those in Fig. 5. Above 750 cm⁻¹, the two spectra in Fig. 6 seem to have no fundamental differences, taking into account the large temperature difference (10 and 140 K). Below 750 cm⁻¹, however, the two spectra exhibit remarkable differences: First, the line *b* is present in PIHS, but not in HTHS. Second, the lines *b'*, *c* and *b''* are apparently shifted toward higher frequency in PIHS. Since no such shifts are observed above 750 cm⁻¹, the shifts of the *b'*, *c* and *b''* lines should not be due to thermal expansion of the crystal as a whole, but due to a local deformation of specific fragments within the crystal structure of Fe-pic.

3.3 Line assignments and discussion

To assign the observed absorption lines to specific vibration modes of Fe-pic, we first compared the observed spectra to the published IR spectra of 2-picolyamine and ethanol.¹²⁾ To distinguish the absorption lines related with the aminomethyl base from those related with the pyridine ring [see Fig. 1(a) and (b)], we compared the published spectra of 2-picolyamine with those of 2-amino-pyridine, 2-methyl-pyridine, and pyridine.¹²⁾ To assign the IR lines to specific vibration modes, we followed the standard guidelines for the IR line assignment of organic compounds.^{13,14)} Characteristic vibration modes of a specific fragment, for example the bending vibration modes of the pyridine ring when it is 2-substituted as in the case of 2-picolyamine, have been known to appear in characteristic frequency bands.^{13,14)}

It was possible to assign most of the observed IR lines to specific vibration modes by these procedures. Table I summarizes the results of the assignment. The lines above 750 cm⁻¹ are due to the C-H deformation modes and the skeletal stretching modes of the picolyamine. For the bands *i* and *j*, the C-H deformation modes within the picolyamine and the ethanol, and the C-N stretching modes of the aminomethyl base overlap.^{13,14)} In contrast, the lines below 750 cm⁻¹ result from the skeletal deformation (bending) of picolyamine, in addition to the low-frequency C-H deformation modes. The lines *b*, *b'* and *b''* in Fig. 5, which show particularly large variations with the SC, could not be assigned with the above procedures only. They were assigned to the skeletal bending modes of -C-C-N- in the aminomethyl base as explained below,

Detailed structure studies of Fe-pic using X-ray diffraction (XRD) have been reported in HTHS and LTLS,¹⁵⁾ and also in PIHS.¹⁶⁾ They have shown the following results: The lattice constants decrease by $\sim 1\%$ from HTHS (150 K) to LTLS (80 K), and increase by $\sim 1\%$ from LTLS to PIHS at 10 K. On the other hand, the average Fe-N distance decreases by $\sim 8\%$ from HTHS (150 K) to LTLS (90 K), and increases by $\sim 9\%$ from LTLS to PIHS at 10 K.¹⁶⁾ Namely, the contraction and the expansion of FeN₆ upon the temperature- and photo-induced SC's are much greater than those of the unit cell. This strong contraction/expansion of FeN₆ is expected to produce a physical pressure on the picolyamine molecules, which bridge two of the six N atoms in the FeN₆ cluster. This will certainly result in a deformation of the picolyamine molecules. Hence the vibration modes of picolyamine actually involving such deformation, *i.e.*, the skeletal vibration modes, are expected to be significantly affected upon the SC; the lines *b*, *b'* and *b''* are likely to result from such vibration modes. The XRD results¹⁶⁾ have also shown that HTHS and PIHS are quite similar in terms of the *average* crystal structure, with the same space group and very close values of lattice constants and average Fe-N distance. Regarding the *local* structure, however, an important difference has been found between PIHS and HTHS by the X-ray absorption near-edge structure (XANES) and extended X-ray absorption fine structure (EXAFS) experiments.¹⁷⁾ Although XANES and EXAFS cannot directly determine the overall crystal structure, they can sensitively probe the local environment of Fe²⁺ ions. Their main results are the following:¹⁷⁾

- (i) The local symmetry at Fe²⁺ is *O_h* in all the three states, *i.e.*, it is kept unchanged in both the temperature- and the photo-induced SC's.
- (ii) The distribution in the distance between Fe²⁺ and the next-nearest-neighbor (nnn) C atoms is slightly different between HTHS and PIHS.

The result (i) shows the absence of Jahn-Teller effect in Fe-pic. Since all the nnn C atoms are contained in the ligand picolyamine, the result (ii) strongly suggests that the picolyamine molecules in PIHS are slightly deformed compared with those in HTHS. Such deformation is probably a consequence of the physical pressure created by the expansion of FeN₆ clusters, and should also be related

with the appearance of the b line in PIHS and the shifts of the b' and b'' lines between PIHS and HTHS. Based on these results from XRD, XANES, and EXAFS, we have assigned the peaks b , b' and b'' to the skeletal bending of the $-C-C-N$ part in the aminomethyl base. It is known^{13,14)} that the C-N stretching modes appear in the range 1050-1300 cm^{-1} . Hence the range 600-700 cm^{-1} is reasonable for the corresponding bending vibrations.

Finally, the l lines in Fig. 5, observed at 2300-2400 cm^{-1} and showing very large variations upon the SC, probably result from overtones and/or coupled modes of lower-frequency lines because no characteristic vibrations are expected in this range for picolylamine and ethanol molecules.¹²⁻¹⁴⁾ However, it is unclear which of the lower-frequency lines have actually resulted in the l lines. In spite of the small intensities, their spectral changes due to temperature- and photo-induced SC's are remarkably clear as shown in Figs. 3 and 5. Hence, the l lines may be due to coupled modes including FeN_6 cluster vibrations. Note that the line energies (approximately 0.3 eV) are too small to be crystal field levels of Fe^{2+} .

The present results based on crystal samples of Fe-pic have shown that the microscopic vibration states undergo very large changes upon the temperature- and photo-induced SC's. These results are reasonable since a change of approximately 8 % in the Fe-N bond length, observed upon the SC, is quite a drastic effect. Therefore, the most remarkable result in the present work is the difference observed in the range 500-720 cm^{-1} between HTHS and PIHS, shown in Fig. 6. This demonstrates that *the two high-spin states involve microscopically different characters*. As already mentioned, the expansion of FeN_6 cluster upon the LTLS $\rightarrow$ PIHS crossover at 10 K is expected to locally create a pressure on the ligand picolylamine. However, such pressure is absent in HTHS. This additional, local pressure on the ligand picolylamine should be responsible for the shifts of lines b' , c and b'' between PIHS and HTHS. Note that they are shifted toward higher frequencies in PIHS by about 10-20 cm^{-1} than in HTHS. These shifts correspond to 3-6 % increases in the effective "spring constants" of these vibration modes, which is a consequence of the local pressure within the picolylamine in PIHS. In addition, the appearance of peak b only in PIHS is quite remarkable. This can be attributed to a loss of inversion center within the unit cell structure in PIHS, since this line has been also observed by Raman spectroscopy in all the three states.¹⁸⁾ (Raman and IR selection rules are exclusive in HTHS and LTLS where the unit cell structure has an inversion center.) Namely, the unit cell structure in PIHS should be slightly deformed from that in HTHS, although the local symmetry around Fe^{2+} is kept O_h , causing the originally IR-inactive b line to appear in PIHS. The slight displacement of nnn C atoms, detected by X-ray absorption, is a most probable candidate for this deformation. The driving force for creating this deformation should be the pressure on picolylamine caused by the FeN_6 cluster.

The local deformation and pressure within the picolylamine ligands, suggested by the present IR and the X-ray absorption experiments,¹⁷⁾ should be very important in understanding the development of PIHS over a macro-

scopic volume in Fe-pic. It should require, as explained in Introduction, a strong, collective interaction among the Fe^{2+} ions and a strong coupling between the Fe^{2+} electronic state and the lattice. Since the X-ray absorption results have shown that the Jahn-Teller effect is absent in Fe-pic, it is very likely that the deformation of picolylamine should play an important role. Note that the picolylamine ligands within a $[\text{Fe}(\text{2-pic})_3]$ complex are hydrogen-bonded to those within the neighboring complexes.¹⁵⁾ Hence the local deformations at the picolylamine ligands caused by the expansion of FeN_6 and the hydrogen bondings connecting the picolylamine ligands at neighboring $[\text{Fe}(\text{2-pic})_3]$ complexes are the most likely origin for the collective interaction among the Fe^{2+} ions. To understand such possibility on a more microscopic basis, however, much more has to be done both experimentally and theoretically. In particular, further experiments in the far-IR region (at frequencies below 450 cm^{-1}) should provide much more insight into the photo-induced variations of microscopic vibration states, since the vibration modes of the FeN_6 clusters should be directly observed. In addition, lower-frequency modes due to FeN_6 and picolylamine are expected to be more sensitive to collective lattice effects. Such experiments are under way.

4. Conclusions

We have presented detailed IR absorption spectra of the spin-crossover complex Fe-pic in its three characteristic states, using single crystal samples for the first time. To overcome the technical difficulty with using the crystal samples, a synchrotron radiation from SPring-8 has been used as an IR source. In addition to the strong absorption lines previously observed with powder samples, we have newly observed many fine lines. Many of the IR lines show strong variations upon temperature- and photo-induced SC's. Most remarkably, some of the lines below 720 cm^{-1} , which are due to the skeletal bending vibrations within the picolylamine ligands, show clear shifts between HTHS and PIHS. This result demonstrates that HTHS and PIHS involve microscopically different characters. In particular, the present results suggest that the picolylamine ligands receive a strong physical pressure upon the photo-induced SC. We have conjectured that such local pressure and the resulting deformation may have led to the collective, long-range interaction needed for the development of macroscopic photo-induced phase, aided by the hydrogen bondings bridging the Fe-pic complexes.

Acknowledgements

We would like to thank M. Matsunami and Y. Kondo for technical assistance. The experiments were performed at SPring-8 under the proposal 2002B0220-CS1-np. This work is partly supported by Grants-In-Aid from the MEXT and by Asahi Glass Foundation.

- 1) A. Hauser, J. Chem. Phys. **94** (1991) 2741.
- 2) P. Gütllich, A. Hauser, H. Spiering, Angew. Chem. Int. Ed. **33** (1994) 2024.

- 3) H. Romstedt, A. Hauser, H. Spiering, J. Phys. Chem. Solids **59** (1998) 265.
- 4) Y. Ogawa, S. Koshihara, K. Koshino, T. Ogawa, C. Urano, H. Takagi: Phys. Rev. Lett. **84** (2000) 3181.
- 5) T. Tayagaki, T. Tanaka: Phys. Rev. Lett. **86** (2001) 2886.
- 6) T. Tayagaki, T. Tanaka: J. Lumines. **94-95** (2001) 537.
- 7) K. Tanaka and T. Tayagaki, Phase Transitions, **75** (2002) 689.
- 8) T. Tayagaki, Master's degree thesis, Kyoto University (2000), unpublished.
- 9) D. Chernyshov, M. Hostettler, K.W. Törnroos, H.-B. Bürgi, Angew. Chem. Int. Ed., **42** (2003) 3825.
- 10) H. Kimura, T. Moriwaki, N. Takahashi, H. Aoyagi, T. Matsushita, Y. Ishizawa, M. Masaki, S. Ohishi, H. Okuma, T. Nanba, M. Sakurai, S. Kimura, H. Okamura, N. Nakagawa, T. Takahashi, K. Fukui, K. Shinoda, Y. Kondo, T. Sata, M. Okuno, M. Matsunami, R. Koyanagi and Y. Yoshimatsu: Nucl. Inst. Meth. Phys. Res. A **467-468** (2001) 441.
- 11) S. Kimura, T. Nanba, T. Sada, M. Okuno, M. Matsunami, K. Shinoda, H. Kimura, T. Moriwaki, M. Yamagata, Y. Kondo, Y. Yoshimatsu, T. Takahashi, K. Fukui, T. Kawamoto, T. Ishikawa: Nucl. Inst. Meth. Phys. Res. A **467-468** (2001) 893.
- 12) C.J. Pouchert, *The Aldrich Library of Infrared Spectra*, Edition III (Aldrich Chemical Company, 1981).
- 13) G. Socrates, *Infrared Characteristic Group Frequencies* (John Wiley & Sons, 1980).
- 14) E. Pretsch, T. Clerc, J. Seibl, W. Simon, *Tables of Spectral Data for Structure Determination of Organic Compounds*, Second Edition (Springer-Verlag, 1981).
- 15) M. Mikami, M. Konno, Y. Saito, Acta. Cryst. **36** (1980) 275.
- 16) N. Huby, L. Guerin, E. Collet, L. Toupet, J.-C. Ameline, H. Cailleau, T. Roisnel, T. Tayagaki, K. Tanaka, Phys. Rev. B,

in press.

- 17) H. Oyanagi, T. Tayagaki, K. Tanaka, AIP Conf. Proc. **652** (2003) 438, and unpublished work.
- 18) T. Tayagaki, K. Tanaka, H. Okamura, Phys. Rev. B, in press.

Table I. Assignment of absorption lines to the specific vibration modes of Fe-pic. The letters in the first column denote the labels for the observed absorption lines in Fig. 5.

Peaks ¹	Fragments ²	Vibration modes
<i>a</i>	am	C-H deformation
<i>b, b', b''</i>	am	skeletal -C-C-N- bending
<i>c</i>	pyr	ring in-plane bending
<i>d, d'</i>	pyr	C-H deformation
<i>e</i>	am	C-H (-CH ₂ -) deformation
<i>f</i>	EtOH	C-H (-CH ₃) deformation
<i>g</i>	pyr	ring in-plane stretching
<i>h</i>	EtOH	-C-OH stretching
<i>i</i>	pyr am	CH in-plane deformation -C-N- stretching
<i>j</i>	am, EtOH	C-H deformation
<i>k</i>	pyr	ring in-plane stretch
<i>l</i>		overtone or coupled.

¹ The peak labels refer to those used in Fig. 5.

² pyr = pyridine ring, am = aminomethyl base, EtOH = ethanol.

Fig. 1. (a) Fe^{2+} and the 2-picolyamine ligands in Fe-pic. (b) A 2-picolyamine (2-aminomethyl pyridine) molecule, which consists of a pyridine ring and an aminomethyl base. (c) Schematic electronic configurations of Fe^{2+} in the high-spin ($S=2$) and in the low-spin ($S=0$) states. The former has a smaller crystal field splitting and a larger Fe-N distance. (d) The fraction of Fe^{2+} ions in Fe-pic in the high-spin state, γ_{HS} , as a function of temperature.⁸⁾ γ_{HS} was determined by the measured magnetic susceptibility.

Fig. 2. Optical absorption spectra of Fe-pic at several temperatures. (The definition of optical density is explained in the text.) Each spectrum is vertically offset by 2. The shaded areas indicate absorption lines that show large temperature variations. Spectral resolution is 4 cm^{-1} .

Fig. 3. Optical absorption spectra of Fe-pic in the $2100\text{--}2500 \text{ cm}^{-1}$ range. The broken curve is the spectrum at 140 K, shown in comparison to that at 40 K. The spectral resolution is 4 cm^{-1} .

Fig. 4. The intensity of several absorption lines in Figs. 2 and 3 as a function of temperature. Each curve shows the intensity integrated over the indicated frequency range, normalized by the difference between 40 and 200 K.

Fig. 5. Optical absorption spectra of Fe-pic in the low-temperature low-spin state (LTLS) and in the photo-induced high-spin state (PIHS) at 10 K. The spectral resolution is 2 cm^{-1} . The labels *a* to *i* indicate the observed absorption lines, and used in the text.

Fig. 6. Optical absorption spectra of Fe-pic in the photo-induced high-spin state (PIHS) at 10 K and in the high-temperature high-spin state (HTHS) at 140 K. Spectral resolution is 2 cm^{-1} . The same labels as those in Fig. 5 are indicated for several absorption lines which exhibit marked differences between the two states.

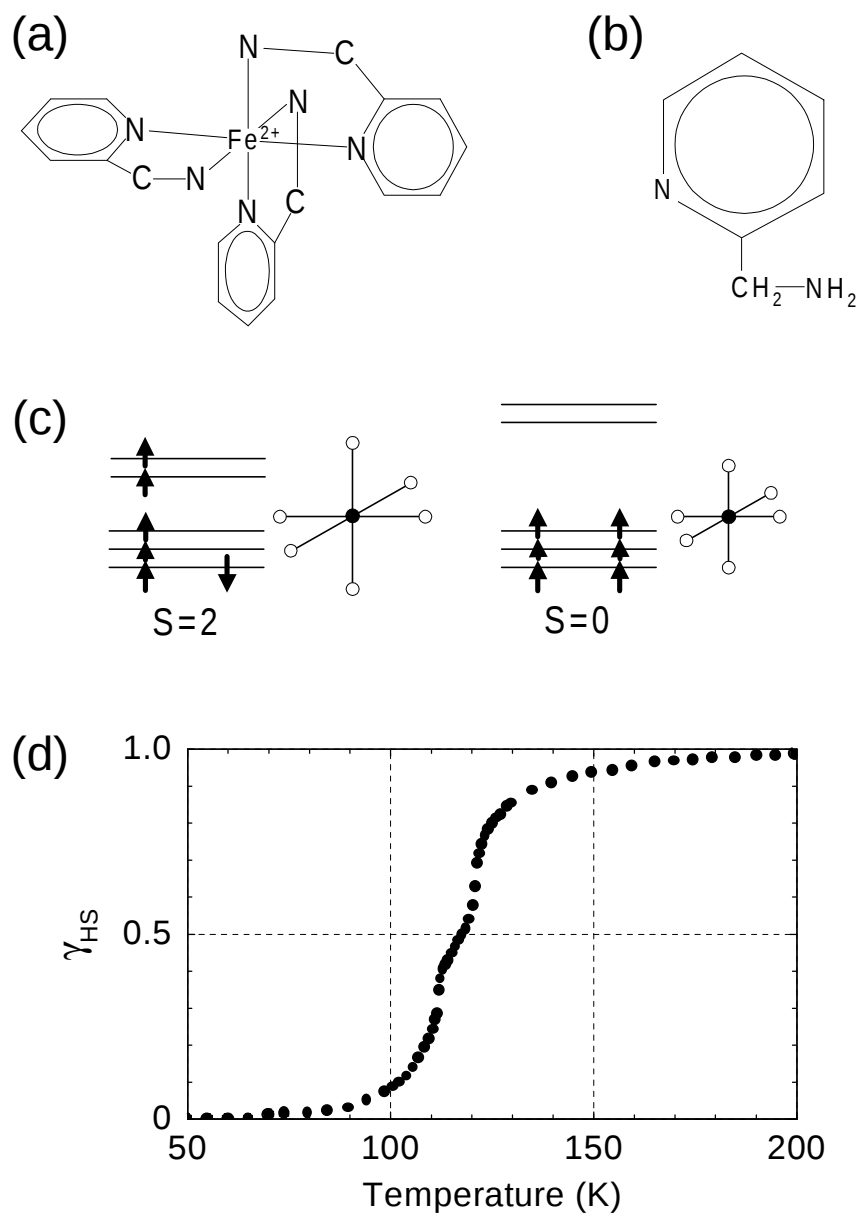


FIG. 1

Okamura et al.

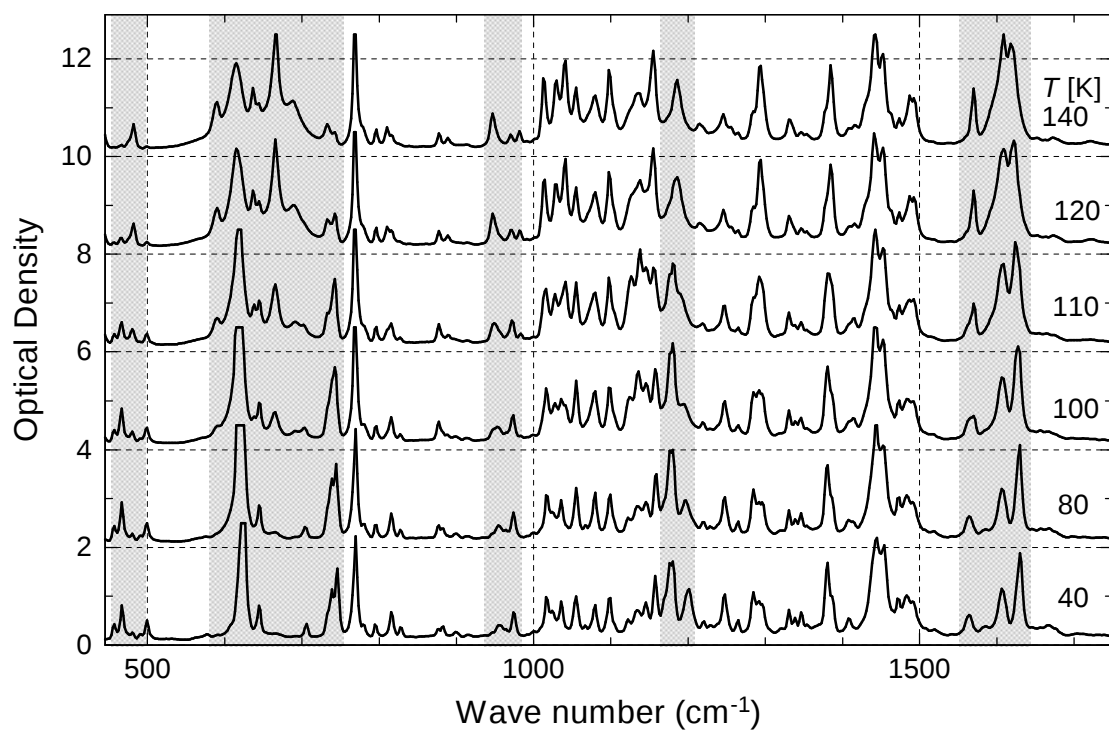


FIG. 2

Okamura et al.

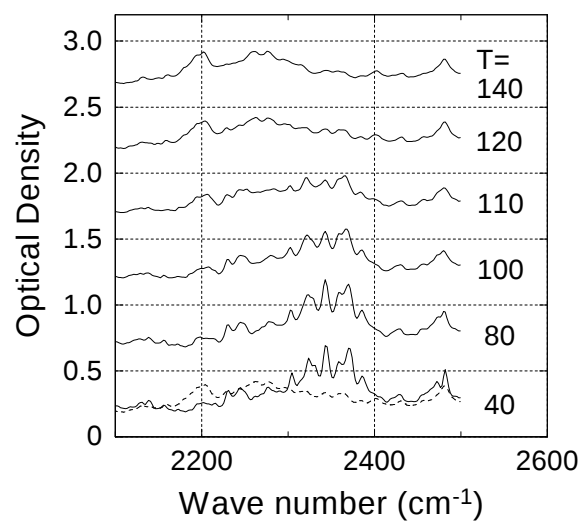


FIG.3
Okamura et al.

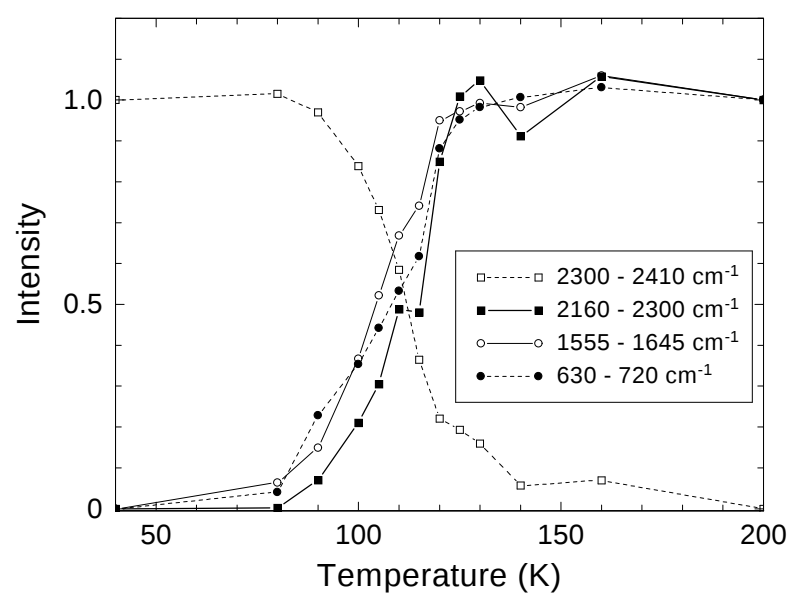


FIG. 4
Okamura et al.

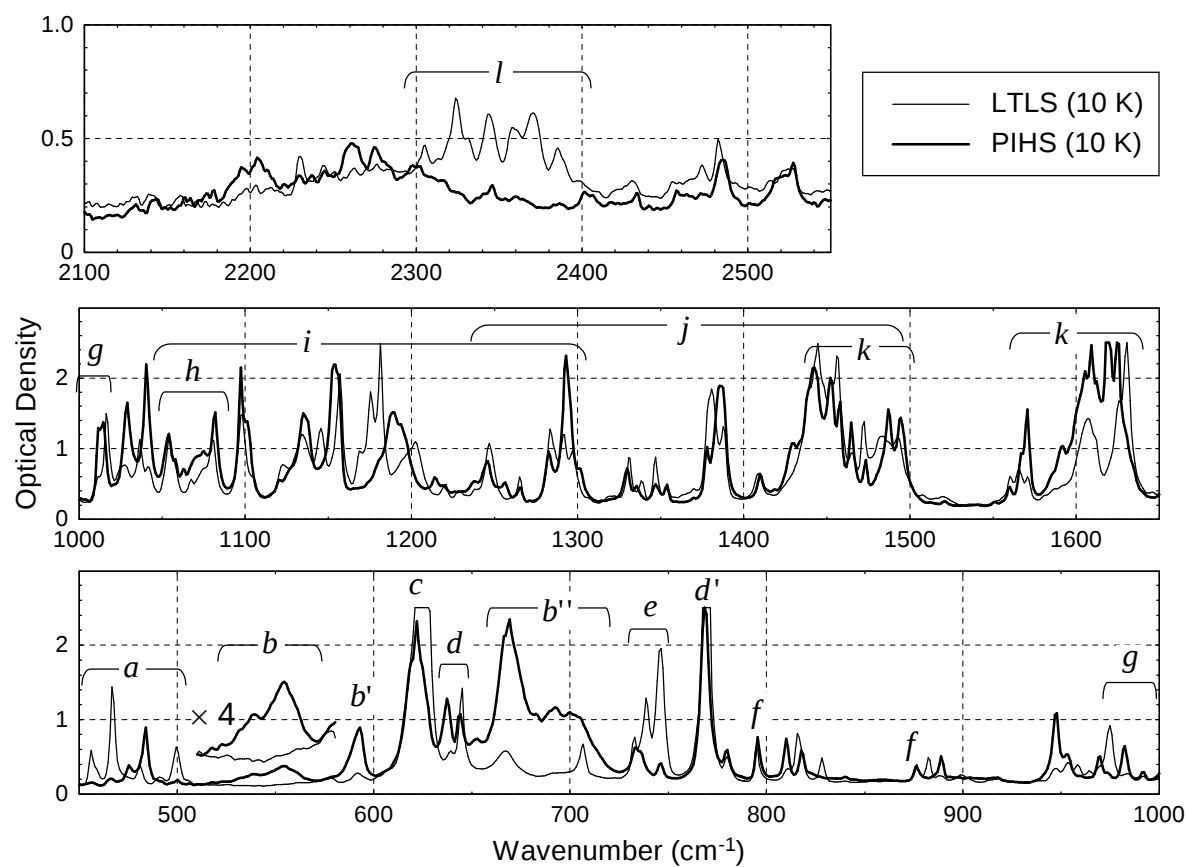


FIG. 5

Okamura et al.

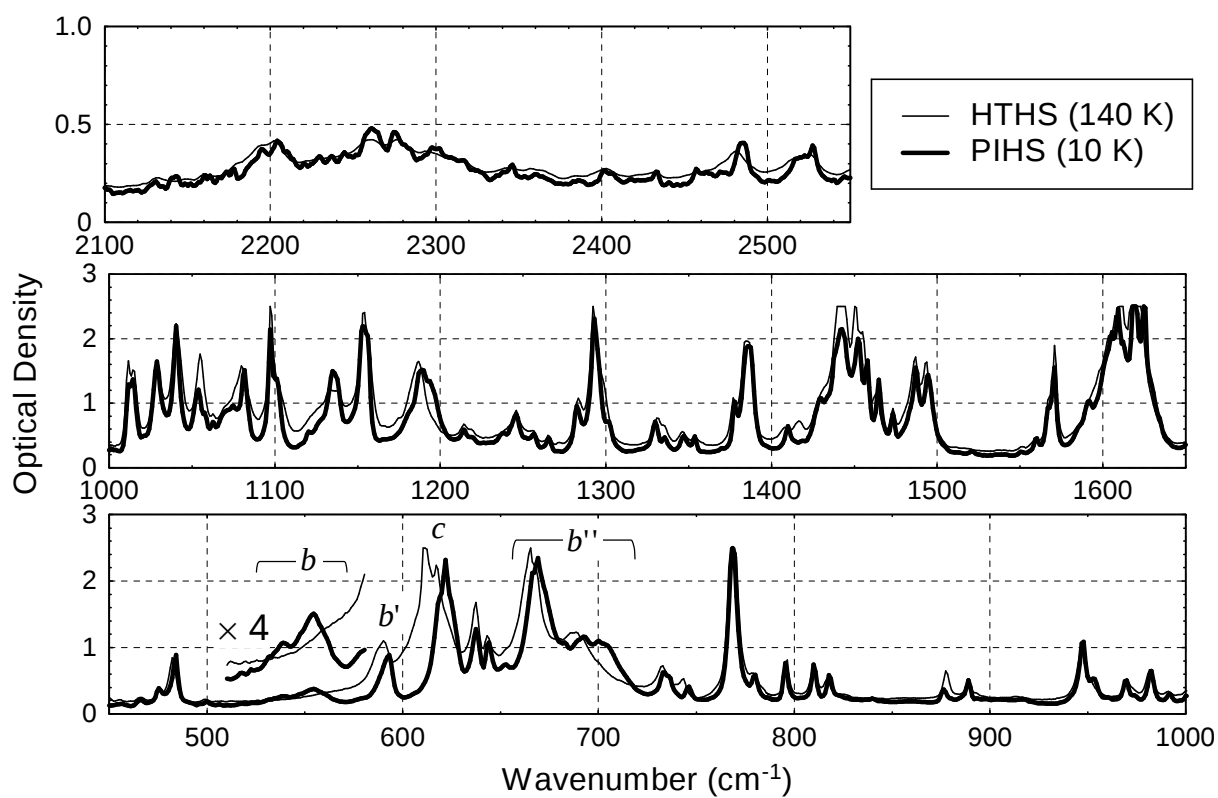


FIG. 6

Okamura et al.